

Physical and Chemical Studies of Taro Starches and Flours^{1,2}

J. JANE,³ L. SHEN,³ J. CHEN,³ S. LIM,³ T. KASEMSUWAN,³ and W. K. NIP⁴

ABSTRACT

Cereal Chem. 69(5):528-535

Taro (*Colocasia esculenta* (L.) Schott) flours were prepared from taro corms of Bun-long, Dasheen, Hawaii Red (Lehua), Hawaii White, and Niu'e varieties. Starch contents of the flours varied from 73 to 76% as determined by enzymatic analysis. Starch yields of the flours varied from 51 to 58%. Nitrogen contents varied from 0.33 to 1.35% and from 0.014 to 0.025% in the flours and starches, respectively. Taro starches had irregular, polygonal shapes and small granular sizes. Among the five varieties, Bun-long starch had the smallest average diameter (2.6 μm), whereas Dasheen starch had the largest (3.76 μm). Amylose contents in these five starch varieties varied from 18 to 22% as determined by iodine affinity and from 19 to 24% as determined by gel permeation chromatography. Molecular sizes of the taro amyloses at the peak of gel permeation chromatography ranged from degree of polymerization (DP) 150 to 550. Branch chain lengths of the taro amylopectin varied

from DP 16.8 to 18.4 and from DP 37.2 to 40.5 for short and long branches, respectively. All five starch varieties gave an A-type X-ray diffraction pattern. The taro starches contained 0.23–0.52% lipid and 0.017–0.025% phosphorus. ³¹P-nuclear magnetic resonance spectra revealed that the phosphorus in the starches was in the form of phosphate monoester derivatives. The onset gelatinization temperatures of the taro flours varied from 72 to 79°C, whereas those of the taro starches ranged from 69 to 74°C. Retrogradations of the starches and the flours, as measured by their enthalpy changes, appeared to be more severe than that of corn starch. Taro starch pastes had significantly higher viscosities than their flour counterparts. Among the varieties, Hawaii Red and Hawaii White starches had the highest peak viscosities, whereas Bun-long starch had the lowest. Both starch and flour pastes set to weak gels.

Taro (*Colocasia esculenta* (L.) Schott) is a tropical tuber crop and is cultivated widely in many countries, including the United States. Taro is a major crop of the islands of Hawaii and Samoa. In Hawaii, taro is cultivated in both wetland and dryland conditions. Native Hawaiians grow taro in wetland for the preparation of poi (taro paste). In addition, taro also has been used in baby food, taro chips, taro bread (Moy and Nip 1983), and taro sorbet (Hong and Nip 1990).

Taro has been reported to have 70–80% starch (dry starch basis, dsb) (Payne et al 1938, Tu et al 1979) with small granules (diameters between 1.4 and 5 μm) (Amin 1955, Sugimoto et al 1986). Taro also is rich in gums (mucilages). Up to 10.7% crude taro mucilages can be extracted from taro corms and tubers with boiling water (Gaind et al 1968). Purified gums (100 g) also are isolated from fresh taro corms (1 kg) (Taki et al 1972). Drum-drying properties and storage stability of tropical fruit-taro mixtures were reported by Nip (1979a,b). The use of crude taro gums as binding and emulsifying agents has been studied by Gaind et al (1968, 1969). Because of its small granular size, taro starch has been considered a good filling agent for biodegradable polyethylene film (Griffin and Wang 1983, Lim et al 1992) and as a fat substitute.

Some chemical and physical properties of several varieties of taro starch, such as Dasheen, Bun-long, Engler, Ishikawa-wase, and Takenokoimo, have been reported (Goering and DeHaas 1972, Higashihara et al 1975, Sugimoto et al 1986). Higher pasting and gelatinization temperatures of taro starches compared with those of other small granular starches, such as cow cockle, catchfly, and pigweed starch, were reported by Goering and DeHaas (1972). Amylose contents of Ishikawa-wase and Takenokoimo taro starch were reported as 13.5 and 10.8%, respectively (Sugimoto et al 1986). Developmental changes in starch properties of taro starches were reported by Sugimoto et al (1987). Taro starch was found more susceptible to pancreatin hydrolysis than other tuber and root starches (Sugimoto et al 1979).

In this study, five varieties of taro flours, Bun-long, Dasheen, Hawaii Red (Lehua), Hawaii White, and Niu'e, were investigated. Chemical structures and physical properties of the flours and starches, including the starch contents and starch yields of the

flours, amylose contents and molecular sizes, amylopectin branch chain lengths, lipid and phosphorus contents, morphology, X-ray diffraction patterns of the starches, protein contents (as nitrogen), thermal properties, retrogradation rates, and pasting and gelling properties of both flours and starches, are reported.

MATERIALS AND METHODS

Porcine pancreatic α -amylase was twice crystallized, and *Aspergillus niger* glucoamylase was lyophilized. Both enzymes and crude α -amylase from *Bacillus* species were purchased from Sigma Chemical Co. (St. Louis, MO). *Pseudomonas* isoamylase was purchased from Hayashibara Shoji, Inc. (Okayama, Japan). Bio-Gel P-6 and Sepharose CL-2B gels were products of Bio-Rad Laboratories (Richmond, CA) and Pharmacia Inc. (Piscataway, NJ), respectively. Pullulan molecular size standards (Shodex P-82 standard) were purchased from Waters (Milford, MA). Other chemicals, all reagent grade, were used without further purification.

Preparation of Taro Flour

Corms from the five varieties of taro—Bun-long (from Hawaii), Dasheen (Hawaii), Hawaii Red (Lehua, Hawaii), Hawaii White (Hawaii), and Niu'e (American Samoa)—were used to prepare taro flours at the Department of Food Science and Human Nutrition, University of Hawaii, Honolulu.

Corms were washed to remove surface soil. The corms from all varieties except Dasheen were hand-peeled and trimmed to remove the skin and defective parts. The Dasheen variety was peeled with an abrasive peeler and hand-trimmed because of small corm size. After peeling and trimming, the corms were cut into smaller pieces before slicing with a Cuisinart food processor equipped with a 0.1-cm ultrathin blade. The slices were dried on perforated trays by using a mechanical convection oven (60°C for 20 hr). The dried slices were ground into flour using a Cross-Beater mill (Glen Mill Corp., Maywood, NJ) equipped with a 0.5-mm screen. The flour was then packed and heat-sealed in laminated bags of about 1 kg each.

The bags were transferred to the Department of Food Science and Human Nutrition, Iowa State University, Ames, for starch isolation and for physical and chemical analyses.

Analysis of Starch Content in the Taro Flour

Taro flour (about 50 mg, dsb) was suspended in 90% dimethyl sulfoxide (3 ml) and boiled in a water bath at 96°C for 1 hr. After cooling, methanol (10 \times) was added to precipitate the solid. The mixture was centrifuged, and the supernatant was discarded. A phosphate buffer solution (pH 6.9, 0.1M, 3 ml) and porcine

¹Journal paper J-14651 and project 2863 of the Iowa Agriculture and Home Economics Experiment Station, Ames.

²Hawaii Institute of Tropical Agriculture and Human Resources journal series 3707.

³Department of Food Science and Human Nutrition, Iowa State University, Ames 50011.

⁴Department of Food Science and Human Nutrition, University of Hawaii at Manoa, Honolulu 96822.

intracooling I system. Aluminum pans (Perkin-Elmer) were used for the analyses. Flour or starch samples (about 2 mg each, dsb) were weighed in the sample pans, mixed with distilled water (about 6 mg), and sealed. The heating rate was 10°C per min. Enthalpy changes, integrated by using DSC-7 standard software, were calibrated on the basis of the melting enthalpy of indium metal. Flour and starch retrogradations were determined by storing the gelatinized samples at 4°C for 28 days. The retrograded samples were analyzed by differential scanning calorimeter and use of the same parameters.

Pasting and Gelling Properties

Pasting curves of taro flours and starches (8% each, dsb) were determined by using a Brabender Visco/Amylograph (model VA-5, 700 cm-g, Hackensack, NJ) operated with a total weight of suspension of 400 g (Smith 1964, Jane et al 1992). The flour and starch suspensions were equilibrated at 30°C and then heated at a rate of 1.5°C/min with constant stirring at 75 rpm. Stirring was continued for 30 min while the paste was held at 97.5°C, and the paste then was cooled to 52.5°C (1.5°C/min). The starch paste was transferred to aluminum pans (5 cm i.d. × 2.5 cm) wrapped with aluminum foil around the wall for additional depth (Takahashi et al 1989). For gel strength analysis, the samples were sealed in plastic bags and stored (25°C for 4 hr and 4°C for 72 hr).

Gel strength of the flour and starch pastes were measured with a Voland texture analyzer (model TA, Scarsdale, NY). Immediately before each measurement, the foil wrap was removed and the surface gel was sliced off with a cheese cutter. This exposed a fresh and smooth surface for texture analysis. A 2-mm-diameter probe and a 3-mm distance of penetration at the speed of 0.2 mm/sec were used through the analysis.

RESULTS AND DISCUSSION

Starch contents of Bun-long, Dasheen, Hawaii Red (Lehua), Hawaii White, and Niu'e taro flours are shown in Table I. The range of the starch contents varied from 73 to 76% (dsb). They are in agreement with the results (70–80%) reported by Payne et al (1938), Higashihara et al (1975), and Tu et al (1979). The starch contents also are similar to that of corn (about 75%). Starch yields from the taro flours (dsb) (Table I) varied from 51 to 58%.

Nitrogen contents of taro flours varied from 0.33% (Hawaii White) to 0.86% (Niu'e) to 1.35% (Dasheen) (Table II). The values are much greater than those found in the starches (0.014–0.025%, Table II). These results indicated that the protein contents of the flours varied from 2.1 to 8.4%, using 6.25 as a conversion factor and providing that all of the nitrogen was from protein. Protein was reported as one of the major components in taro mucilage (Yamashita and Yoshikawa 1973). Therefore, the nitrogen in the flour can be attributed to its mucilage. The nitrogen content in the flour also appeared to correlate with wetland and dryland cultivation. The results indicated that dryland cultivated varieties (i.e., Dasheen and Niu'e) had significantly higher nitrogen contents than the wetland cultivated varieties (Table II). The isolated starches (without the removal of protein by toluene and NaCl solution) contained only 0.09–0.16% protein, which suggested that the starches were fairly pure.

Scanning electron micrographs showed that taro starch granules had polygonal and irregular shapes with diameters of 1–5 μm (Fig. 1). The results agreed with those reported by Sugimoto et al (1986, 1987). The shapes of the granules suggested that they were compound starches. Diameters of taro starches analyzed by the image analyzer are shown in Table III. The results are in agreement with those reported by Amin (1955) and Sugimoto et al (1986). In addition, our results also indicated that, among the five varieties, Bun-long starch had the smallest granular size; equivalent circle diameters varied from 0.3 to 4.3 μm, with an average diameter of 2.6 ± 0.73 μm. Dasheen starch had the largest granular size; equivalent circle diameters varied from 0.4 to 6.9 μm, with an average diameter of 3.76 ± 1.18 μm. All of the taro starches were significantly smaller than corn starch (5–20 μm) and potato starch (30–100 μm) and were similar to small-granule wheat starch (Lineback 1984).

Small granular starch has been demonstrated to be a good filler for biodegradable plastic film (Lim et al 1992) and also has been suggested to provide a better mouth feeling as a lipid substitute (Daniel and Whistler 1990). Taro starch granules tended to coagulate (data not shown), which resulted in rough surface textures when used in starch-filled biodegradable plastic film (unpublished data from our laboratory). These coagulation tendencies may be attributable to the gum residues that remain on the surface of the starch granules, even though, on the basis of detected nitrogen content (Table II), the amount of gum was low (0.09–0.16%).

Starch amylose contents determined by IPT (Schoch 1964b) and by GPC (Colonna and Mercier 1984) were in reasonably good agreement. They varied from 18 to 22% and from 19 to 24% by IPT and GPC methods, respectively (Table IV). Among the varieties, Dasheen and Bun-long taro starches had greater amylose contents than the others, whereas Hawaii White and Hawaii Red had the smallest. Results obtained from the GPC method were, in general, greater than those obtained from the IPT method. The difference can be attributed to the presence of the intermediate components, molecules with branched structures and molecular sizes smaller than amylopectin, which were eluted at the same time as amylose. The amylose content of taro starch is similar to that of potato starch (about 20%) but lower than that of corn starch (28–30%) (Lineback 1984).

Gel permeation chromatograms showed that the molecular sizes of amyloses differed (Fig. 2). The peak molecular sizes of the taro amyloses varied between degree of polymerization (DP) 150 and 550, which are smaller than that of potato (DP 1,500) and of corn (DP 667) as calculated by K_{av} and using pullulan standards (Jane and Chen 1992). The low blue value that appeared in the Bun-long amylopectin peak (Fig. 2A) indicated that Bun-long amylopectin had short branch chains compared with those of the other varieties.

Branch chain lengths of taro amylopectins and their distributions are shown in Table V. The peak chain lengths of short branch chains (A and short B chains), which were similar to those of corn amylopectin, varied between DP 16.8 and 18.4. The chain lengths of long branch chains (long B chains) varied between DP 37 and 40. Bun-long taro had the shortest branch chains (DP 16.8 and 37.2 for short and long branches, respectively) among all the taro starches. These results were consistent with

TABLE III
Granular Size of Taro Starch Determined by the Image Analyzer^a

Source	Area (μm ²)	Diameter, μm		
		Maximum	Minimum	Equivalent Circle
Bun-long	5.74 ± 2.92	3.08 ± 0.83	2.55 ± 0.78	2.60 ± 0.73
Dasheen	12.16 ± 6.99	4.26 ± 1.33	3.69 ± 1.21	3.76 ± 1.18
Hawaii Red	7.43 ± 3.33	3.40 ± 0.76	2.94 ± 0.71	3.00 ± 0.68
Hawaii White	7.01 ± 3.91	3.27 ± 1.00	2.85 ± 0.90	2.86 ± 0.86
Niu'e	9.20 ± 5.90	3.72 ± 1.11	3.18 ± 1.09	3.26 ± 1.05

^aAverage of 205 granule samples.

TABLE IV
Amylose Content in Taro Starch^a

Sample	IPT ^b (%)	GPC ^c (%)
Bun-long	22.1 ± 0.1	23.5 ± 0.9
Dasheen	22.2 ± 0.3	24.3 ± 0.8
Hawaii Red	18.1 ± 0.1	19.8 ± 0.9
Hawaii White	18.5 ± 0.2	19.2 ± 0.9
Niu'e	19.6 ± 0.2	20.1 ± 0.8

^aAverage of two replicates.

^bIodine potentiometric titration.

^cGel permeation column chromatography using Sepharose CL-2B gel.

the low blue value observed in the Bun-long amylopectin peak (Fig. 2A). All five taro starches gave the A-type X-ray diffraction pattern (Fig. 3). This diffraction pattern agreed with that of the starch with short branch chain amylopectin (Hizukuri et al 1983,

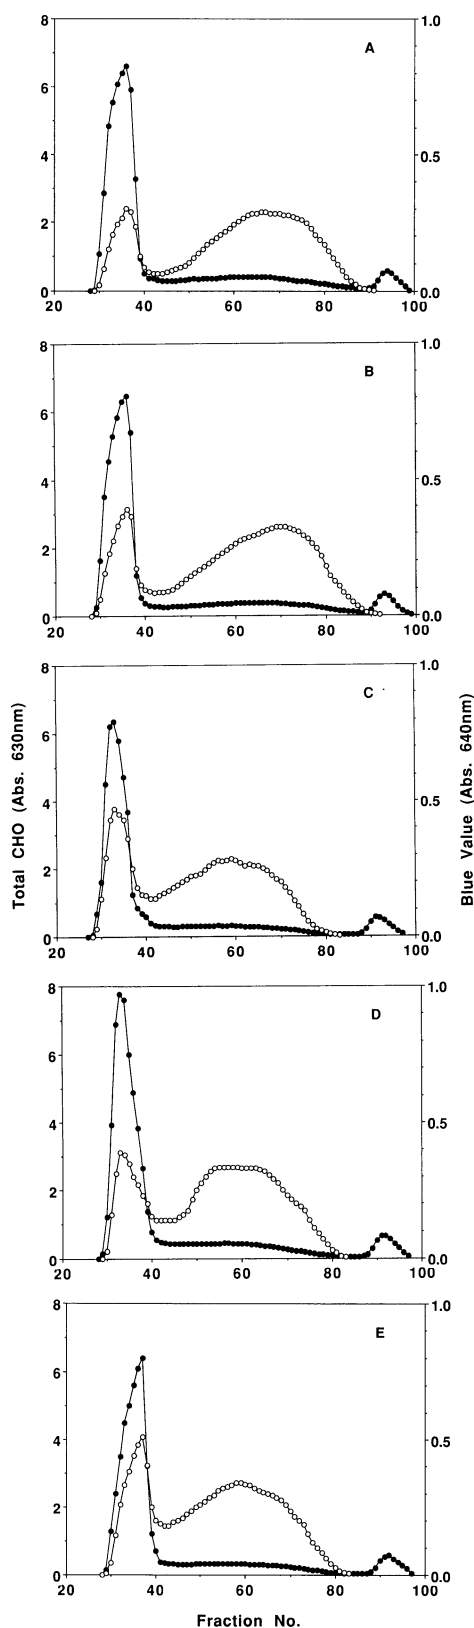


Fig. 2. Gel permeation chromatograms of taro starches as determined using a Sepharose CL-2B column (2.6 cm i.d. \times 75 cm) and a NaCl (0.02%) solution as the eluent, 5 ml per fraction. Total carbohydrate (●) was analyzed by anthrone-sulfuric acid method, and blue value (○) was analyzed by iodine staining. Glucose was used as a marker. A, Bun-long; B, Dasheen; C, Hawaii Red; D, Hawaii White; E, Niu'e.

Hizukuri 1985).

Lipid contents of taro starches varied from 0.24 to 0.52% (Table VI), which were less than that of corn starch (0.81%) analyzed by the same procedure. Phosphorus contents of the defatted taro starches varied from 0.017 to 0.025%, which was similar to that of defatted corn starch (0.017%) and significantly lower than that of potato starch (0.07%). However, ^{31}P -nuclear magnetic resonance spectra of all the taro starches showed signals at 3.99, 4.20, and 4.47 ppm (Fig. 4), corresponding to the phosphate monoester derivatives on C-6 (3.99 and 4.20 ppm) and C-3 (4.47 ppm) of glucose units (Lim 1990, Lim and Seib 1990). The spectra were similar to those of potato starch and indicated that the phosphorus in the taro starches was in the form of phosphate monoester derivatives. The small signal at 2.92 ppm (Fig. 4) was that of free phosphate. In contrast, the spectrum of normal corn starch exhibited a major signal at 0.061 ppm, which coincided with the signal of phospholipids (unpublished data from our laboratory). Spectra of other taro starches were identical and, thus, not shown.

Differential scanning calorimetric studies of taro flours and starches showed that the gelatinization temperatures of the flours (72.3–79.0°C) (Table VII) were higher than those of the starches (69.1–74.0°C) (Table VIII). The difference could be attributed to the presence of mucilage in the flours. In addition to protein, the mucilage also contains complex polysaccharides such as arabinogalactan (Taki et al 1972). The polysaccharide could compete with starch for moisture and result in a higher onset starch gelatinization temperature in the flour.

TABLE V
Branch Chain Length^a and Distributions of Taro Amylopectin^b

Source	Long Branch Chain		Short Branch Chain	
	Chain Length ^c	Percent	Chain Length ^c	Percent
Bun-long	37.2 \pm 0.2	22.7 \pm 0.2	16.8 \pm 0.2	77.3 \pm 0.2
Dasheen	39.6 \pm 1.2	21.5 \pm 1.5	18.4 \pm 0.5	78.6 \pm 1.6
Hawaii Red	38.4 \pm 0.6	21.2 \pm 1.5	18.0 \pm 0.3	78.8 \pm 1.5
Hawaii White	38.2 \pm 0.6	22.0 \pm 0.8	18.1 \pm 0.3	78.0 \pm 0.8
Niu'e	40.5 \pm 0.0	19.0 \pm 0.2	17.4 \pm 0.2	81.1 \pm 0.1

^a Measured in degrees of polymerization.

^b Average of two replicates.

^c The chain length was determined by using peak fractions.

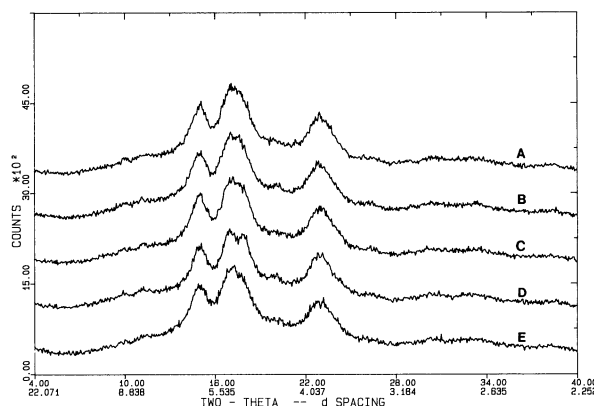


Fig. 3. X-ray diffraction patterns of the starches of taro varieties Bun-long, Dasheen, Hawaii Red, Hawaii White, and Niu'e (A–E, respectively).

TABLE VI
Lipid and Phosphorus Contents of Taro Starch^a

Sample	Lipid (%)	Phosphorus (%)
Bun-long	0.25 \pm 0.02	0.021 \pm 0.001
Dasheen	0.38 \pm 0.01	0.025 \pm 0.011
Hawaii Red	0.36 \pm 0.01	0.017 \pm 0.004
Hawaii White	0.24 \pm 0.02	0.025 \pm 0.002
Niu'e	0.52 \pm 0.03	0.020 \pm 0.006

^a Average of two replicates.

Among the taro flours and starches, Bun-long taro had the lowest onset gelatinization temperatures: 72.3 and 69.1°C for flour and starch, respectively. Retrogradations of taro starches after being stored at 4°C for 28 days were more severe than that of corn starch as measured by enthalpy changes (Table VIII). The small amylose molecules of taro starches (Fig. 2) may be responsible for the severe retrogradation (Jane and Chen 1992). Retrograded Bun-long flour and starch also showed the lowest

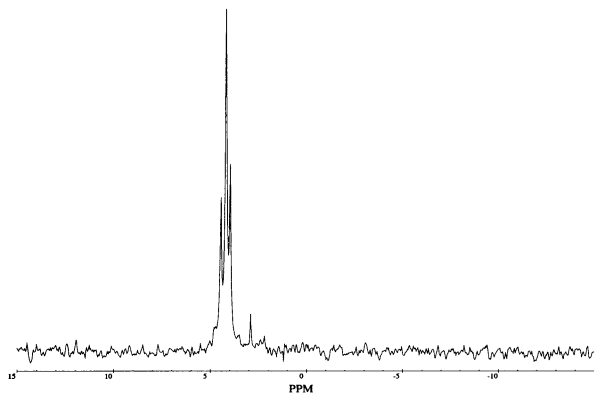


Fig. 4. ³¹P-nuclear magnetic resonance spectrum of Hawaii White taro starch hydrolyzed by *Bacillus* α-amylase. The solution was adjusted to pH 8, and the chemical shifts were referenced to external H₃PO₄ (85%) at 0.0 ppm.

TABLE VII
Thermal Property of Taro Flour^a

Source	Gelatinization Temperature, ^b °C			ΔH ^c (J/g)
	T _o	T _p	T _c	
Native flour				
Bun-long	72.3 ± 0.2	77.3 ± 0.1	85.6 ± 0.6	11.9 ± 0.2
Dasheen	78.6 ± 0.2	83.5 ± 0.1	92.4 ± 0.2	11.6 ± 0.1
Hawaii Red	77.4 ± 0.2	81.5 ± 0.2	90.1 ± 0.1	11.8 ± 0.4
Hawaii White	77.4 ± 0.2	81.3 ± 0.1	89.1 ± 0.2	12.0 ± 0.1
Niu'e	79.0 ± 0.0	83.0 ± 0.1	90.8 ± 0.1	12.2 ± 0.4
Retrograded flour ^d				
Bun-long	39.0 ± 0.7	49.5 ± 0.1	61.4 ± 1.4	5.2 ± 0.6
Dasheen	46.3 ± 0.2	57.5 ± 0.1	65.7 ± 0.1	3.3 ± 0.1
Hawaii Red	46.2 ± 0.1	56.2 ± 0.6	65.4 ± 0.5	5.0 ± 0.1
Hawaii White	45.7 ± 0.5	57.3 ± 0.5	66.1 ± 0.6	5.6 ± 0.1
Niu'e	45.0 ± 0.1	57.3 ± 0.3	66.1 ± 0.5	4.7 ± 0.2

^a Average of three replicates.

^b T_o, onset temperature; T_p, peak temperature; T_c, complete temperature.

^c Enthalpy change.

^d After 28 days at 4°C.

TABLE VIII
Thermal Property of Taro Starch^a

Source	Gelatinization Temperature, ^b °C			ΔH ^c (J/g)
	T _o	T _p	T _c	
Native starch				
Bun-long	69.1 ± 0.0	73.6 ± 0.3	83.0 ± 0.1	15.5 ± 0.1
Dasheen	74.0 ± 0.6	79.0 ± 0.3	93.1 ± 0.3	14.0 ± 0.3
Hawaii Red	72.0 ± 0.6	76.6 ± 0.6	89.2 ± 0.2	15.2 ± 0.3
Hawaii White	72.2 ± 0.8	78.6 ± 0.9	90.5 ± 1.2	13.6 ± 0.6
Niu'e	74.0 ± 0.5	77.9 ± 0.3	88.7 ± 0.2	14.2 ± 0.8
Corn	66.5 ± 0.5	72.4 ± 0.4	82.0 ± 0.4	12.1 ± 0.5
Retrograded starch ^d				
Bun-long	39.6 ± 0.7	48.5 ± 0.1	57.7 ± 0.2	6.3 ± 0.6
Dasheen	45.0 ± 0.5	54.2 ± 0.2	65.9 ± 0.7	7.2 ± 0.4
Hawaii Red	43.2 ± 0.6	52.6 ± 0.6	63.2 ± 1.2	5.9 ± 1.0
Hawaii White	44.0 ± 1.0	54.0 ± 0.5	64.8 ± 0.7	7.3 ± 0.2
Niu'e	43.8 ± 0.2	53.4 ± 0.5	65.0 ± 0.5	7.3 ± 0.2
Corn	44.0 ± 0.8	51.6 ± 0.6	61.0 ± 0.4	3.7 ± 0.3

^a Average of three replicates.

^b T_o, onset temperature; T_p, peak temperature; T_c, complete temperature.

^c Enthalpy change.

^d After 28 days at 4°C.

onset temperatures (39.0 and 39.6°C, respectively). These consistent low onset temperatures can be attributed to the short branch chain lengths of Bun-long amylopectin (Table V). It is plausible that the shorter branch chain lengths (particularly the long B chains) of Bun-long amylopectin (Table V) were responsible for the significantly lower gelatinization temperatures of the starch (69.1 and 39.6°C for native and retrograded starches, respectively) (Table VIII) and the flour (72.3 and 39.0°C for native and retrograded flours, respectively) (Table VII) compared with those of other taro starches and flours.

The pasting properties of taro flours and starches are shown in Figures 5 and 6, respectively. At the same solid concentration level, the starch pastes displayed much greater viscosity than their flour counterparts. Pasting temperatures of the flour pastes (76–80°C) also were significantly higher than those of the starch pastes (70–75°C). The differences also can be attributed to the presence of mucilage. Among the flours, Dasheen flour had the highest peak viscosity and pasting temperature. This is consistent with its high mucilage content, reflected by both the high baseline of the amylogram and the high nitrogen (protein) content (Table II). Among the starch pastes, Hawaii White and Hawaii Red displayed the highest peak viscosity (about 1,400 BU), whereas

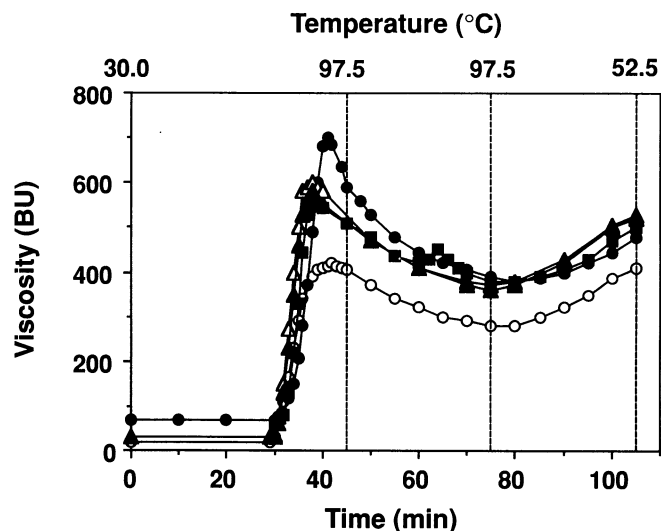


Fig. 5. Pasting properties of taro flours as measured by the Brabender Visco/Amylograph. The flours were prepared from taro corms of varieties Bun-long (○), Dasheen (●), Hawaii Red (△), Hawaii White (▲), and Niu'e (■).

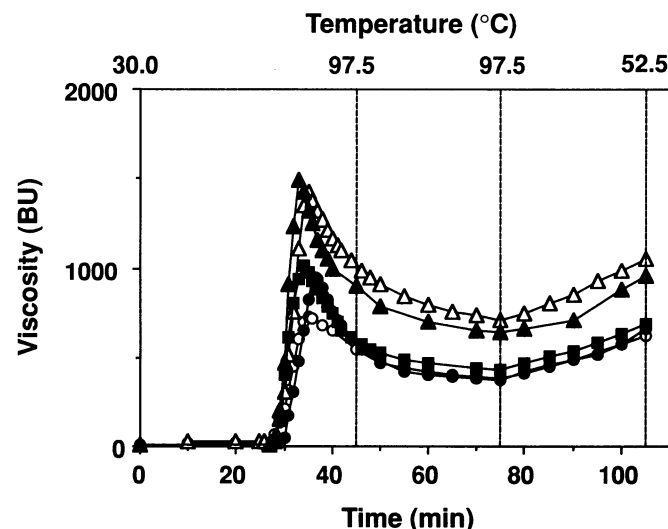


Fig. 6. Pasting properties of taro starches as measured by the Brabender Visco/Amylograph. The starches were isolated from flours of taro varieties Bun-long (○), Dasheen (●), Hawaii Red (△), Hawaii White (▲), and Niu'e (■).

TABLE IX
Gel Strength^a of Taro Flour and Starch Pastes^b

Source	Flour		Starch	
	4 hr at 25°C	72 hr at 4°C	4 hr at 25°C	72 hr at 4°C
Bun-long	1.5 ± 0.1	2.0 ± 0.1	1.9 ± 0.1	2.7 ± 0.2
Dasheen	1.3 ± 0.1	1.8 ± 0.1	1.5 ± 0.1	2.4 ± 0.1
Hawaii Red	1.2 ± 0.1	1.6 ± 0.1	1.5 ± 0.1	1.9 ± 0.1
Hawaii White	1.2 ± 0.1	1.6 ± 0.1	1.5 ± 0.1	2.1 ± 0.2
Niu'e	1.2 ± 0.1	1.4 ± 0.1	1.5 ± 0.1	1.8 ± 0.1

^a Measured in grams.

^b Average of two replicates on an 8% dry starch basis.

Bun-long taro had the lowest (about 700 BU). The low amylose contents of Hawaii Red and Hawaii White starches (Table IV) may contribute to the high viscosities and the low pasting temperatures of the pastes, whereas the high amylose contents of Bun-long and Dasheen starches resulted in the low viscosities and the high pasting temperatures of the pastes as well as the greater gel strength (Table IX). It is also plausible that the combination of the short branch chain lengths of Bun-long amylopectin (Table V) and high amylose content (Table IV) was responsible for the lowest viscosity exhibited by Bun-long starch paste. This is consistent with the effects of branch chain lengths of amylopectin on the viscosities of starch pastes reported by Jane and Chen (1992).

Taro starch pastes set to weak gels. After being stored at 4°C for 72 hr, strengths of the gels varied from 1.8 to 2.7 g, which were substantially lower values than that of corn starch (about 10 g). The phosphate monoester derivatives of the taro starches are believed responsible for the soft gels observed for the starches. The taro flour pastes prepared and stored under the same conditions displayed even weaker gel strength (1.4 to 2.0 g). Among the varieties, Bun-long and Dasheen taro flours and starches set to the strongest gels; this was directly correlated with their higher amylose contents compared with those of other varieties (Tables IV and IX). The weak (soft) gels might be desirable for uses in frozen foods and desserts.

Significant differences were found between the varieties of the taro flours as well as between the starches. It is known that Bun-long, Hawaii Red, and Hawaii White varieties were wetland cultivated and that Dasheen and Niu'e were dryland cultivated. Both Dasheen and Niu'e flours had very high protein contents. Niu'e starch also had very high lipid content (Table VI). Whether the soil moisture conditions affected these properties of taro is not clear. A comparison study using the same variety cultivated under different conditions will help to clarify the effects of soil moisture.

In conclusion, the five varieties of taro starches were different in their granular sizes. The starches had different amounts of amylose and different branch chain lengths of amylopectin, which resulted in their differences in pasting properties and gelatinization temperature. The starches had fairly low lipid contents (except Niu'e) and low phosphorus contents from phosphate monoester derivatives. All five starch varieties gave the A-type X-ray diffraction pattern. All of the flours displayed higher gelatinization temperatures and lower paste viscosities than those of their starch counterparts. High mucilage (protein) content in Dasheen flour resulted in a greater viscosity and a higher pasting temperature than those of other flours in the study.

ACKNOWLEDGMENT

We acknowledge the funding source from the Governor's Agriculture Coordinating Committee of the State of Hawaii, project 90-06.

LITERATURE CITED

- AMIN, E. S. 1955. The polysaccharides of *Colocasia antiquorum*. J. Chem. Soc. (Lond.) p. 2411.
 CARROLL, J. J., SMITH, N., and BABSON, A. L. 1970. A colorimetric serum glucose determination using hexokinase and glucose-6-phosphate

- dehydrogenase. Biochem. Med. 4:171.
 COLONNA, P., and MERCIER, C. 1984. Macromolecular structure of wrinkled- and smooth-pea starch components. Carbohydr. Res. 126:233.
 DANIEL, J. R., and WHISTLER, R. L. 1990. Fatty sensory qualities of polysaccharides. (Abstr.) Cereal Foods World 35:825.
 DUBOIS, M., GILLES, K. A., HAMILTON, J. K., REBERS, P. A., and SMITH, F. 1956. Colorimetric method for determination of sugars and related substances. Anal. Chem. 28:350.
 GAIND, K. N., CHOPRA, K. S., and DUA, A. C. 1968. Study of mucilages of corm and tuber of *Colocasia esculenta* Linn. Part I. Emulsifying properties. Indian J. Pharm. 30:208.
 GAIND, K. N., CHOPRA, K. S., and DUA, A. C. 1969. Study of mucilages of corm and tuber of *Colocasia esculenta* Linn. Part II. Binding properties. Indian J. Pharm. 31:156.
 GOERING, K. J., and DeHAAS, B. 1972. New starches. VIII. Properties of the small granule-starch from *Colocasia esculenta*. Cereal Chem. 49:712.
 GRIFFIN, G., and WANG, J.-K., 1983. Industrial uses. Page 301 in: Taro: A Review of *Colocasia esculenta* and Its Potentials. J.-K. Wang, ed. University of Hawaii Press: Honolulu.
 HIGASHIHARA, M., UMEKI, K., and YAMAMOTO, T. 1975. Isolation and some properties of taro root starch. J. Jpn. Soc. Starch Sci. 22:61.
 HIZUKURI, S. 1985. Relationship between the distribution of the chain length of amylopectin and the crystalline structure of starch granules. Carbohydr. Res. 141:295.
 HIZUKURI, S., KANEKO, T., and TAKEDA, Y. 1983. Measurement of the chain length of amylopectin and its relevance to the origin of crystalline polymorphism of starch granules. Biochim. Biophys. Acta 760:188.
 HIZUKURI, S., TAKEDA, Y., and YASUDA, M. 1981. Multi-branched nature of amylose and the action of debranching enzymes. Carbohydr. Res. 94:205.
 HONG, G. P., and NIP, W. K. 1990. Functional properties of precooked taro flour in sorbets. Food Chem. 36:261.
 JANE, J., and CHEN, J. 1992. Effect of amylose molecular size and amylopectin branch chain length on paste properties of starch. Cereal Chem. 69:60.
 JANE, J., SHEN, L., and AGUILAR, F. 1992. Characterization of pejobaye starch. Cereal Chem. 69:96.
 JULIANO, B. O. 1971. A simplified assay for milled-rice amylose. Cereal Sci. Today 16:334.
 LEE, E. Y. C., MERCIER, C., and WHELAN, W. J. 1968. A method for the investigation of the fine structure of amylopectin. Arch. Biochem. Biophys. 125:1028.
 LIM, S. 1990. Preparation and properties of a thick-boiling, phosphorylated wheat starch for food use, and location of phosphate esters on starch by ³¹P-nmr spectroscopy. Ph.D. thesis. Kansas State University: Manhattan.
 LIM, S., and SEIB, P. A. 1990. Position of phosphorylation in a wheat starch phosphate and in potato starch determined by ³¹P-NMR spectroscopy. (Abstr.) Cereal Foods World 35:825.
 LIM, S., JANE, J., RAJAGOPALAN, S., and SEIB, P. A. 1992. Effect of starch granule size on physical properties of starch-filled polyethylene film. Biotechnol. Progr. 8:51.
 LINEBACK, D. R. 1984. The starch granule organization and properties. Baker's Dig. 17.
 MOY, J. H., and NIP, W. K. 1983. Processed food. Page 261 in: Taro: A Review of *Colocasia esculenta* and Its Potentials. J.-K. Wang, ed. University of Hawaii Press: Honolulu.
 NIP, W. K. 1979a. Development and storage stability of drum-dried guava- and papaya-taro flakes. J. Food Sci. 44:222.
 NIP, W. K. 1979b. Drum-dried pineapple-taro and mango-taro flakes. Page 266 in: Small Scale Processing and Storage of Tropical Root Crops. D. L. Plucknett, ed. Westview Press: Boulder, CO.
 PAYNE, J. H., LEY, G. J., and AKAU, F. 1938. Processing and chemical investigations of taro. Hawaii Agric. Exp. Stn. Bull. 86.
 SCHOCH, T. J. 1964a. Fatty substances in starch. Page 56 in: Methods in Carbohydrate Chemistry. Vol. 4. R. L. Whistler, ed. Academic Press: Orlando, FL.
 SCHOCH, T. J. 1964b. Iodimetric determination of amylose. Potentiometric titration: Standard method. Page 157 in: Methods in Carbohydrate Chemistry. Vol. 4. R. L. Whistler, ed. Academic Press: Orlando, FL.
 SMITH, R. J. 1964. Viscosity of starch pastes. Page 114 in: Methods in Carbohydrate Chemistry. Vol. 4. R. L. Whistler, ed. Academic Press: Orlando, FL.
 SMITH, R. J., and CARUSO, J.-L. 1964. Determination of phosphorus. Page 42 in: Methods in Carbohydrate Chemistry. Vol. 4. R. L. Whistler, ed. Academic Press: Orlando, FL.

